

Comment on “Triplet-to-Singlet Exciton Formation in poly(p-phenylene-vinylene) Light-Emitting Diodes”

Lin *et al.* claim to have determined the ratio γ of triplet to singlet excitons in poly(p-phenylene-vinylene) (PPV) light emitting diodes by measuring the singlet and triplet absorption spectra under conditions of optical and electrical excitation¹. The authors find that (a) $\gamma \gg 3$ at weak electric fields, and (b) $\gamma < 3$ at moderate electric fields. This steep electric field dependence and $\gamma < 3$ at moderate fields is explained assuming: (i) initial formation of a high energy triplet T_2 from the triplet electron-hole (e-h) pair, which lies slightly below the e-h continuum and which is dipole allowed from the lowest triplet T_1 , (ii) a phonon bottleneck² in the nonradiative relaxation from T_2 to T_1 , due to the large energy gap between them, and (iii) the competing field-induced dissociation of the T_2 exciton, and the consequent suppression of γ . The authors quote reference 3 to state that since the higher energy singlet exciton S_2 is only 0.3 eV above S_1 , phonon bottleneck and field induced dissociation are absent in the singlet channel.

The lowest excitations in PPV can be simulated within the Pariser-Parr-Pople model for linear polyenes with artificially large effective bond alternation⁴,

$$H = - \sum_{i,\sigma} t(1 \pm \delta)(c_{i\sigma}^\dagger c_{i+1,\sigma} + h.c.) + U \sum_i n_{i\uparrow} n_{i\downarrow} + \sum_{i < j} V_{ij} (n_i - 1)(n_j - 1) \quad (1)$$

where all terms have their usual meanings. Using the standard U and t , Ohno parametrization for V_{ij} and $\delta = 0.24$ we have calculated the exact singlet and triplet energies for the chain with $N = 12$ atoms. In Fig. 1, we show the exact triplet energy spectrum between T_1 , hereafter $1^3B_u^-$, and the dipole-coupled T_2 , hereafter $1^3A_g^+$. We have also included the optical singlet exciton S_1 ($1^1B_u^-$) and the singlet exciton $m^1A_g^+$, which has the largest transition dipole with the $1^1B_u^-$ within (1) (the quantum number m is N -dependent and is 8 in $N = 12$)⁵, and is closer to the e-h continuum⁶ than the $1^3A_g^+$. The $m^1A_g^+$ is observable in nonlinear spectroscopy^{5,7} which places this state above the S_2 state calculated in reference 3 and cited by Lin *et al.* The S_2 state in reference 3 is the lowest two-photon state $2^1A_g^+$ of PPV and not the $m^1A_g^+$. The energy gap between the $m^1A_g^+$ and the $1^1B_u^-$ is at least as dense as that between the $1^3A_g^+$ and the $1^3B_u^-$, and hence there exist singlet excitons nearly degenerate with $1^3B_u^-$. The large energy of the $1^1B_u^-$ and the large energy gaps in Fig. 1 are finite size effects. With

increasing N , absolute energies as well as energy differences decrease rapidly⁵ and additional levels appear in the energy gaps. Different theoretical treatments have confirmed this picture of the long chain limit^{8,9}.

Two conclusions emerge from Fig. 1. First, the triplet

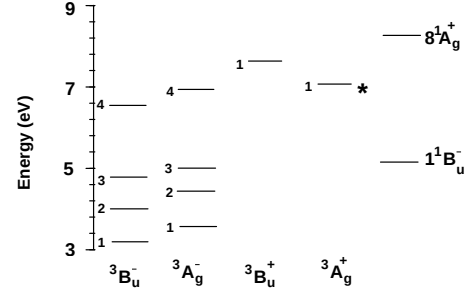


FIG. 1: The triplet energy spectrum between the $1^3B_u^-$ and the $1^3A_g^+$ in a $N = 12$ chain relative to the singlet ground state. Different symmetry subspaces are shown separately. State marked by asterisk is dipole-coupled to the $1^3B_u^-$. The $1^1B_u^-$ and the $m^1A_g^+$ ($m = 8$ in $N = 12$) are also included.

spectrum between T_1 and the lowest dipole connected triplet, the so called T_2 in reference 2 is very dense in long chains. Absorption measurements miss all the dipole-forbidden states in between. Hence the phonon bottleneck in the nonradiative relaxation^{1,2} will not occur. The observed field dependence¹ of γ therefore cannot be explained within Lin *et al.*'s model. Second, the formation of the $1^3B_u^-$ triplet exciton via the $m^3A_g^+$ would imply similar formation of the $1^1B_u^-$ singlet exciton via the $m^1A_g^+$. If indeed the energy spectra were sparse, contradicting our calculations, then exciton dissociation would be larger in the singlet channel due to the closer proximity of the $m^1A_g^+$ to the e-h continuum. This would have caused a field dependence of γ opposite to what is observed by the Lin *et al.*¹. Our theoretical results therefore cast severe doubts on Lin *et al.*'s model, and by implication on the experimental results themselves.

This work was partially supported by NSF and DST.

S. Mazumdar
Department of Physics
University of Arizona, Tucson, AZ 85721

Mousumi Das and S. Ramasesha
Solid State and Structural Chemistry Unit
Indian Institute of Science, Bangalore 560012, India.

¹ L.C. Lin *et al.*, Phys. Rev. Lett. **90**, 036601 (2003).

² T.M. Hong and H.F. Meng, Phys. Rev. B **63**, 075206 (2001).

³ M. Rohlfing and S. Louie, Phys. Rev. Lett. **82**, 1959 (1999).

⁴ Z.G. Soos *et al.*, Chem. Phys. Lett. **194**, 341 (1992).

- ⁵ D. Guo *et al.*, Phys. Rev. B **48**, 1433 (1993).
⁶ Y. Shimoi and S. Mazumdar, Synth. Metals **85**, 1027 (1997).
⁷ M. Liess *et al.* Phys. Rev. B **56**, 15712 (1997).
⁸ S. Abe *et al.* Phys. Rev. B **45**, 9432 (1992).
⁹ A. Race *et al.* Phys. Rev. B **64**, 035208 (2001).